

Comment on “Microscopic theory of network glasses”

In a recent Letter Hall and Wolynes[1] (HW) ask whether a microscopic theory of network glasses can be developed starting from a model of dense spherical fluids. To do so they constrain the number of nearest neighbors and count their central force interactions separately. They obtain the dynamical transition temperature T_A (below which the system is nonergodic and the motion is landscape-determined), and the entropy crisis (Kauzmann) temperature T_K as functions of n_b , the average number of nearest neighbor bonds/atom. A Lindemann melting criterion on the amplitude of nearest neighbor vibrations defines the glass transition temperature T_G . The model shows that T_A/T_G and T_K/T_G monotonically increase and decrease, respectively, as functions of n_b . For $n_b = 2.4$, $T_A/T_G = 100$, an unreasonable result. Mode coupling theory (MCT) defines a critical nonergodicity temperature T_c beyond which a radical change in the long time limit of e.g. the density-density correlation function occurs. T_c has been plausibly estimated for vitreous silica in molecular dynamics simulations[2] as $T_c/T_G = 2$. Even this temperature is presently outside the reach of experimental investigations[2].

How do these results compare with experiments ? There are standard procedures for extrapolating specific heats to obtain T_K , but identifying the onset of nonergodicity at T_A (or T_c) is much more difficult. Chalcogenide glasses are ideal test systems because one can synthesize them over a wide range of n_b by chemical alloying group IV additives in Se base glass. Fortunately, glass transitions of these systems have been recently reinvestigated [3] using modulated DSC (MDSC), a new method which permits separating the usual DSC heat flow endotherm $\dot{H}_T$ into a reversing part $\dot{H}_{rev}$ which is ergodic (and which follows the modulated T-profile) from the non-reversing part $\dot{H}_{nr}$ which is non-ergodic (arising from underlying temperature dependent activated processes) as illustrated in Fig.1a. MDSC permits to establish this temperature T_A at which dynamics become landscape dominated (i.e. in MDSC language dominated by a T-dependent $\dot{H}_{nr}$) in contrast to the linear response regime (i.e. at high temperatures when the heat flow is $\dot{H}_{rev}$ dominated with a constant activation energy).

In binary Ge_xSe_{1-x} glasses, observed variations in T_A/T_G and T_K/T_G as a function of $n_b = 2 + 2x$ are compared to HW predictions in Fig.1b. The $T_K/T_G(n_b)$ results were obtained from a Vogel-Fulcher analysis of viscosity measurements[4]. And one finds the observed and predicted variations in $T_K/T_G(n_b)$ ratio to be in reasonable accord with each other showing a general reduction starting from a value of about 0.9 at $n_b = 2$ to a value of 0.8 near $n_b = 2.7$. Note, however, that the broad global minimum in the observed T_K/T_G ratio near $n_b = 2.4$ is not reproduced by the HW approach. More serious is the fact that observed T_A/T_G values are (i) *two orders of*

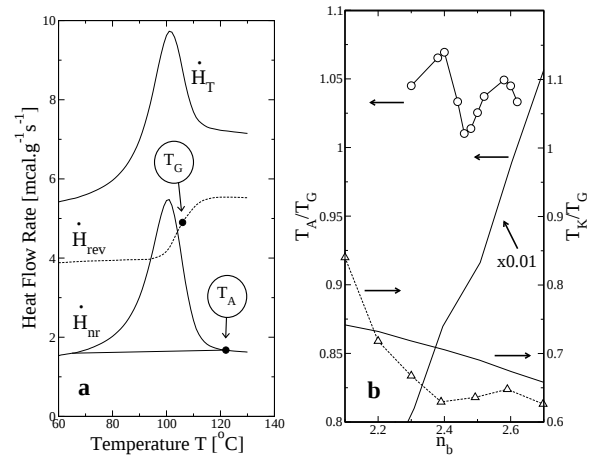


FIG. 1: a: MDSC scan of $As_{20}Se_{80}$ bulk glass; T_G is defined as inflexion point of $\dot{H}_{rev}$ while T_A is the end point of the $\dot{H}_{nr}$ endotherm. b: T_A/T_G ($\circ$) and T_K/T_G ($\triangle$) for Ge-Se glasses. Lines without symbols are HW predictions [1]

magnitude lower than the HW predictions and (ii) show a global minimum near $n_b = 2.4$ that is in sharp contrast to the almost linear increase (Fig. 1b) predicted by HW. The global minimum in T_K/T_G and T_A/T_G ratios are features related to self-organization of glasses that are missing in the HW approach. Clearly features such as inclusion of *local structures*[3, 5], *structural self-organization*[5, 6] and *non-central forces* (bond-bending) are missing in the theory. Non-bending forces constitute $(4n_b - 6)/(5n_b - 6)$ of the global number of network constraints (e.g. 0.6 at the ideal $n_b = 2.4$) indicating that the directional non central angular forces have to be included in a successful theory of network glasses.

M. Micoulaut¹ and P. Boolchand²

¹ LPTL, Université Paris VI, 4, place Jussieu 75252 Paris Cedex 05, France

² Department of ECECS, University of Cincinnati, Cincinnati, Ohio 45221-0030

PACS numbers: 61.43.Fs, 64.70.Pf

-
- [1] R.W. Hall and P. G. Wolynes, Phys. Rev. Lett. **90** 85505 (2003)
 - [2] J. Horbach and W. Kob, Phys. Rev. **E64**, 041503 (2001); W. Kob, M. Nauroth, and F. Sciortino, J. Non-Cryst. Solids **107**, 181 (2002)
 - [3] X. Feng, W. Bresser, P. Boolchand, Phys. Rev. Lett. **78** 4422 (1997); Y. Wang, J. Wells, D.G. Georgiev, P. Boolchand, K. Jackson, M. Micoulaut, Phys. Rev. Lett. **87** 5503 (2001).
 - [4] C.A. Angell, in Rigidity Theory and Applications, M.F. Thorpe, P.M. Duxbury Eds. (Plenum Press, Kluwer Academic, New York, 1999).
 - [5] M. Micoulaut, J.C. Phillips, Phys. Rev. **B67** 104204 (2003); J.C. Phillips, Phys. Rev. Lett. **88** 216401 (2002).

- [6] P. Boolchand, D.G. Georgiev, B. Goodman, J. Optoelectronics and Adv. Mater. **3**, 703 (2001)